

Interplay between Freezing and Superconductivity in the Optimally Doped $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ under Hydrostatic Pressure

B.Simović,^{1,*} M. Nicklas,^{1,†} P.C. Hammel,² M. Hücker,³ B. Büchner,⁴ and J. D. Thompson¹

¹*Condensed Matter and Thermal Physics, Los Alamos National Laboratory, Los Alamos, NM 87545*

²*Department of Physics, The Ohio State University, Columbus, OH 43210*

³*Physics Department Brookhaven National Laboratory, Upton, New York 11973*

⁴*RWTH Aachen, Aachen Germany*

(Dated: February 2, 2008)

We study the electronic properties of a $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ single crystal under hydrostatic pressure up to 2.9 GPa. Both the freezing of the Cu 3d moments and the structural transition from the orthorhombic (LTO) to the tetragonal (LTT) phase are observed via the relaxation of the nuclear magnetization of ^{139}La nuclei. Resistivity and magnetic susceptibility measurements have been carried out under pressure on the same sample. The combination of all data reveals the connection between glassy dynamics, charge localization and the disappearance of superconductivity in the LTT phase.

PACS numbers: 74.72.Dn, 74.25.Ha, 74.62.Fj, 33.25.+k

The phenomenon of charge-stripe ordering in hole-doped antiferromagnets has received much attention since its discovery in $\text{La}_{1.48}\text{Nd}_{0.4}\text{Sr}_{0.12}\text{CuO}_4$ by elastic neutron scattering. [1] Much of this interest has been motivated by the proximity between stripe order and high temperature superconductivity and the potential relationship between these two states. [2, 3, 4] It is now accepted that competing electronic interactions can stabilize charge-stripe order, but the question of whether the order observed in $\text{La}_{1.48}\text{Nd}_{0.4}\text{Sr}_{0.12}\text{CuO}_4$ is a genuine electronic phenomenon or specific to a particular distortion of the CuO_2 plane remains controversial.

Evidence for stripe ordering have been reported so far in the lanthanum cuprates $\text{La}_{2-x-y}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ [1, 5] and more recently in $\text{La}_{2-x}\text{Ba}_x\text{CuO}_4$. [6] These compounds undergo a first order transition from an orthorhombic (LTO) to a tetragonal (LTT) phase which affects superconductivity dramatically at optimal hole doping. [7] In both phases, the CuO_6 octahedra tilt collectively toward the c-axis of the perovskite structure. [7] This distortion produces a staggered buckling of the CuO_2 plane with a symmetry different for LTO and LTT phases. [7, 8] Stripe order emerges in lieu of superconductivity when the tilt exceeds $\approx 3.6^\circ$ in the LTT phase. [1, 9]

Despite those observations, the reason for the disappearance of superconductivity is not understood. Neutron-scattering experiments in $\text{La}_{2-x-y}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ have shown that the stripe arrangement mimics, to some extent, the symmetry of the tilt pattern of the LTT phase, and the detection of the stripe order in this compound is coincident with the first order structural transition. [1] This suggests strong pinning of the charge-stripe order by the underlying lattice, which tends to localize charge carriers. Yet, this picture appears incomplete for $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ where signs of ordering of the Cu 3d moments are observed only below 30K, while

the LTT phase occurs at $T_{\text{LT}}=135\text{K}$. [8, 10, 11] Neutron scattering has failed so far to find evidence of charge-stripe order in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ but the slow dynamics of the Cu 3d moments, probed by NMR at low temperature, has been shown to be consistent with the picture of a glass-forming charge-stripe liquid state [11]. This is indicative of strong frustration, which could also be detrimental to superconductivity.

To clarify the relation between freezing, superconductivity and structural distortion, we use pressure to change the buckling of the CuO_2 plane without modifying doping or substitutional disorder. We have investigated a $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ single crystal under pressure up to 2.9 GPa by means of the magnetization relaxation rate $^{139}\text{T}_1^{-1}$ of the ^{139}La nuclear spins, the magnetic ac susceptibility χ_{ac} and the in-plane resistivity ρ_{ab} . The pressure-temperature phase diagram of $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ is obtained from the pressure dependence of four distinct quantities. First, the freezing temperature, T_{ω_0} , is defined from the maximum of $^{139}\text{T}_1^{-1}$ where the frequency scale Ω of the magnetic hyperfine field fluctuations at the La site equals the Larmor frequency ($\omega_0 = 50\text{MHz}$) of the ^{139}La nuclear spins. Second, the temperature T_{LT} also is determined from $^{139}\text{T}_1^{-1}$ through its response to fluctuations of the surrounding electric field gradient near the first order structural transition [12]. Third, the superconducting transition temperature T_c is determined from the temperature dependence of χ_{ac} . Fourth, the amplitude of the upturn in ρ_{ab} observed below 100K measures the tendency for charge carriers to localize on lowering temperature. This study shows as a whole that the disappearance of superconductivity in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ originates from long-time dynamical properties of the charge inhomogeneous phase. This anomalous long-time behavior appears to be controlled by the amplitude of the buckling of the CuO_2 layer which decreases under pressure.

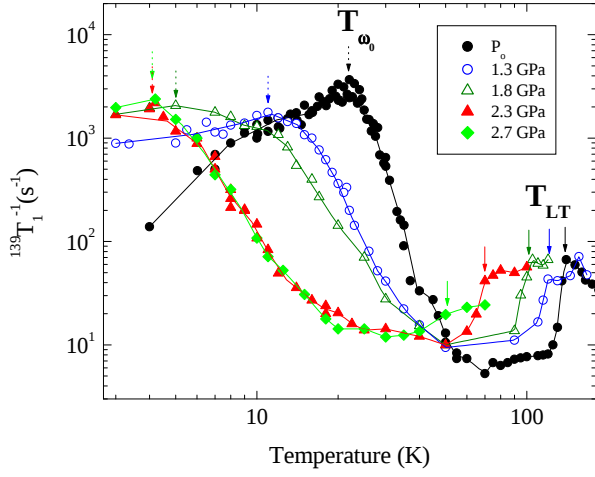


FIG. 1: $^{139}T_1^{-1}$ versus temperature measured at different pressure. T_{LT} and T_{ω_0} are marked with solid and dotted arrows respectively. We find that $dT_{\omega_0}/dP = -9 \text{ K.GPa}^{-1}$ up to $P = 1.8 \text{ GPa}$. The same fitting procedure as proposed in ref [11] has been used to extract the relaxation rates from the magnetization recovery

These findings show that frustration plays a central role in the sharp suppression of superconductivity in the LTT phase of $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$.

This study has been carried out on the same single crystal used in ref [8, 11]. Two similar clamp-type cells were used to generate hydrostatic pressure and, in both cases, fluorinert served as pressure medium. The pressure inside the cell was determined at room temperature by measuring the resistivity of a calibrated manganin gauge located next to the sample. Lowering the temperature from 300 to 4 K induces pressure losses of $\approx 0.3 \text{ GPa}$. [13] The $^{139}\text{La}(I = 7/2)$ NMR measurements were made on the central ($m_I = +\frac{1}{2} \leftrightarrow -\frac{1}{2}$) transition. $^{139}T_1^{-1}$ was measured up to 2.7 GPa by monitoring the recovery of the magnetization after an inversion pulse in a field of 83.5 kOe. After completing NMR experiments, the resistivity and magnetic susceptibility measurements were carried out simultaneously up to 2.9 GPa.

Fig.1 shows the temperature dependence of the relaxation rate $^{139}T_1^{-1}$ for different values of pressure. The features observed at ambient pressure (P_0) have been examined already and discussed in detail [11]. They can be summarized as follows. The discontinuous drop of $^{139}T_1^{-1}$ around $T_{LT} \approx 135 \text{ K}$ indicates the occurrence of the first order structural transition from LTO to LTT. The broad peak in the relaxation rate $^{139}T_1^{-1}$ manifests a gradual freezing of the hyperfine field induced at the La site by the Cu 3d localized moments. We thus read from Fig.1 the pressure dependence of T_{LT} and T_{ω_0} and we observe that both decrease continuously with increasing pressure. It is striking, however, that T_{ω_0} saturates near 3 K for $P \gtrsim 1.8 \text{ GPa}$ while T_{LT} continues to decrease at higher pres-

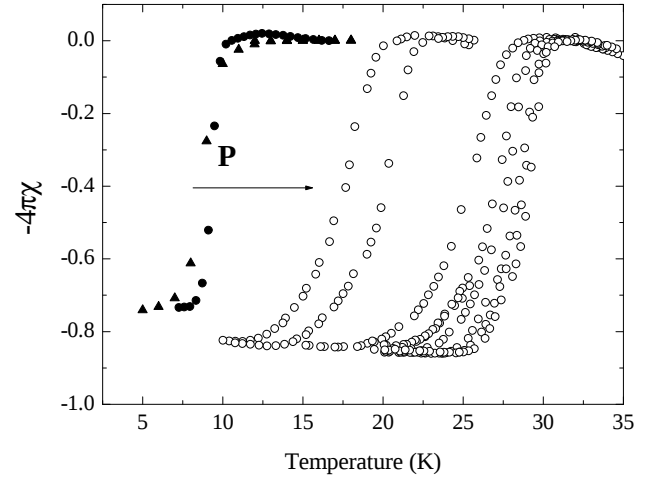


FIG. 2: Diamagnetic shielding versus temperature for the successive following pressure (empty circles): 0.67, 1.17, 1.66, 1.75, 1.97, 2.27, 2.51 and 2.9 GPa. At P_0 , the diamagnetic shielding has been measured after depressurization from 3.0 GPa (full circles) and the measurement at P_0 was repeated 4 months later (full triangles).

sure. Fig.1 makes it obvious that $^{139}T_1^{-1}(T)$ below 30 K is unchanged between 2.3 and 2.7 GPa, whereas T_{LT} is reduced by a factor of two. These differences establish the remarkable fact that the properties of the freezing of the Cu 3d moments no longer depend on the underlying lattice at high pressure.

When looking at Fig.1, a question arises as to whether the temperature of the glass transition, T_g , remains finite or drops to zero under pressure. It should be emphasized that T_g is conceptually different from T_{ω_0} . Insofar as T_{ω_0} indicates only the temperature at which $\Omega \approx \omega_0$, it can relate to dynamical properties at thermal equilibrium whereas T_g marks the onset of a fully static non-equilibrium state, the system being frozen out into a glass.

The relation between T_{ω_0} and T_g is *a priori* unknown but the two temperatures clearly differ at P_0 where $T_g \lesssim 5 \text{ K}$ and $T_{\omega_0} \approx 25 \text{ K}$ [11]. From $^{139}T_1^{-1}$ alone, we can not determine the value of T_g since $^{139}T_1^{-1}$ measures only the spectral weight of the fluctuations at frequencies close to ω_0 . Nevertheless, it can be seen in Fig.1 that the broad maximum of $^{139}T_1^{-1}$ occurs around 3 K at high pressure. This means that $\Omega \approx \omega_0$ in this temperature range while the system is frozen out at P_0 . Therefore, T_g has dropped significantly and, hence disappearance of the glass phase under pressure is conceivable but remains to be proven. This said, one should keep in mind that despite the pressure dependence of $^{139}T_1^{-1}$ revealing a considerable enhancement of the Cu 3d moments fluctuations with increasing pressure, dynamics still remains extremely slow ($\approx 10^{-7} \text{ eV}$) compared to typical electron time scales. In particular, at low temperature, dynamics is certainly

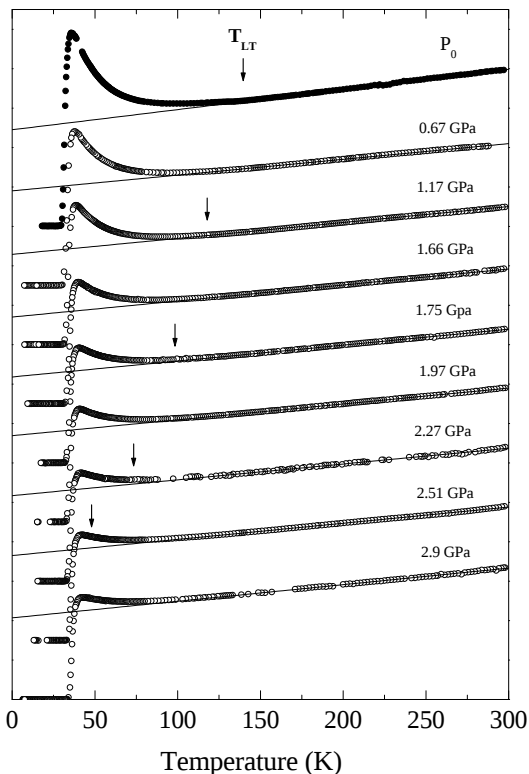


FIG. 3: ρ_{ab} versus temperature at P_0 (full circles) and at higher pressure (empty circles). ρ_{ab} at P_0 was measured after depressurization from 3.0 GPa. The continuous lines are linear fits described in the text and the solid arrow shows the temperature T_{LT} when available from NMR data. The sharp drop at 30K shows filamentary superconductivity in our sample.

faster at pressures higher than P_0 but would nonetheless appear as static on the time scale ($\gtrsim 1$ meV) of neutron-diffraction experiments. Thus, the variation seen in Fig.1 reflects properties of the inhomogeneous phase *over long time scales* i.e $\tau \gtrsim \omega_0^{-1}$.

We show the amplitude of the diamagnetic shielding in Fig.2. Shielding of the applied magnetic field (equal to 10 Oe) manifests the presence of superconductivity in our $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ single crystal and Fig.2 makes clear that T_c increases under pressure. We find that $dT_c/dP = 12 \pm 1$ K.GPa $^{-1}$ for $P < P_s = 1.5 \pm 0.15$ GPa and reduces to 0.6 ± 0.2 K.GPa $^{-1}$ above. We emphasize, however, that the pressure dependence of the volume fraction of superconductivity cannot be inferred unambiguously from the data of Fig.2.

The resistivity ρ_{ab} measured in the CuO_2 plane, is shown in Fig.3. We analyze the data as follows. For each value of pressure, we fit ρ_{ab} in the temperature interval 150-300K to the linear form $\rho_0 + \gamma T$ and extract the quantity $\rho_{UP}(T) = \rho_{ab}(T) - \rho_0 - \gamma T$. We find that the residual term ρ_0 varies smoothly with pressure. At P_0 , $\rho_0 = 2.5 \pm 0.001$ m Ω .cm and decreases at the rate of

-0.13 m Ω .cm.GPa $^{-1}$. The slope of the linear term, $\gamma = 5.08 \pm 0.02$ $\mu\Omega$.cm at P_0 and drops to 4.03 ± 0.02 at 0.67 GPa, which is the first pressure point in our experiment. γ remains unchanged at higher pressure, the variation being less than 0.4%.

This linear term in the resistivity is typical of the metallic phase of optimally doped cuprates. It is considered to be an evidence for a non-Fermi liquid behavior, which might be related to a quantum-phase transition at $T = 0$. [14] In $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ it can be seen in Fig.3 that this feature is unaffected by pressure.

Most of the effect of increasing pressure on ρ_{ab} is reflected in the amplitude of the upturn. This upturn is characteristic of the LTT phase around optimal Sr doping and its amplitude increases with rare-earth substitution. [9, 15]. Because superconductivity is suppressed also with increasing rare-earth content, the upturn might be related to a competing order, but the mechanism by which localization occurs is still unknown. Nevertheless, we can estimate the amplitude of the upturn from Fig.3 as the maximum of the term ρ_{UP} . We find that it decays as e^{-P/P_s} with $P_s = 1.5 \pm 0.1$ GPa, as shown in the lower panel of Fig.4.

The relevance of P_s becomes clear when comparing T_{LT} , T_c , T_{ω_0} and the maximum of ρ_{UP} as a function of pressure in Fig.4. We discern two distinct regimes on either side of P_s , which differ in the way variations of T_{LT} alter the electronic properties of the CuO_2 layer. To better appreciate the role of the lattice, we compare T_c and T_{LT} as a function of Eu content in $\text{La}_{2-x-y}\text{Eu}_y\text{Sr}_x\text{CuO}_4$ [15] with that obtained in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ under pressure, in the inset of Fig.4. The correspondence between the two sets of data is clear: increasing pressure is equivalent to reducing Eu content and, by the same token, to the buckling of the CuO_2 layer [9]. It is, therefore, the amplitude of the structural distortion that controls the interplay between freezing and superconductivity in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$. However, the two compete with each other only when $P \leq P_s$, where T_{LT} varies slowly with pressure. Above P_s , the two phenomena no longer interfere and, both freezing and superconductivity depend only weakly on pressure. Since the temperature T_{LT} is connected to the amplitude of the staggered buckling of the CuO_2 layer [9], the sharp contrast above P_s between the rapid drop of T_{LT} and the saturation of T_c and T_{ω_0} reveals the important conclusion that the coexistence between slow dynamics of the Cu 3d moments and superconductivity at high pressure is electronic in origin. Also, the slow dynamics and the presence of buckling of the CuO_2 layer do not limit T_c which reaches its optimal value above P_s . It is then clear that the key insight provided by our work is that the mechanism of the dramatic suppression of T_c in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ is to be found in the long time ($t \gtrsim \omega_0^{-1}$) dynamical properties of the inhomogeneous phase at low pressure or equivalently, at

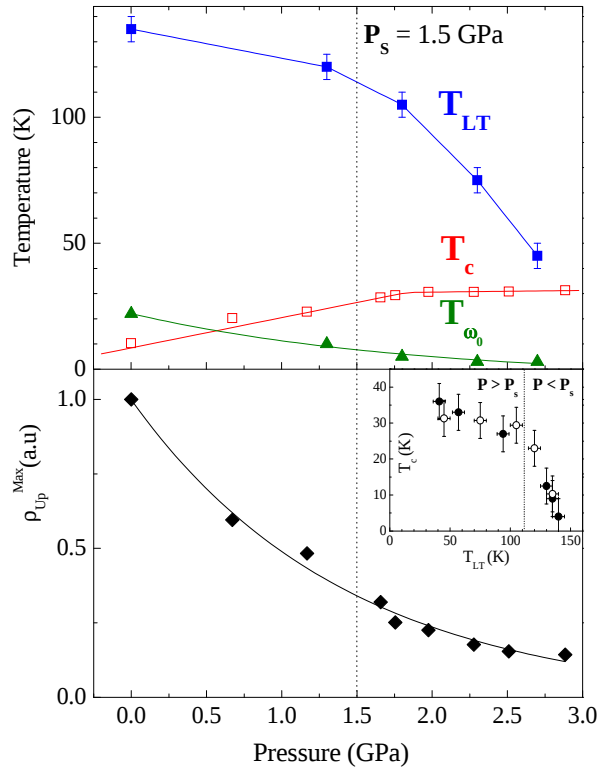


FIG. 4: Overall phase diagram of $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$. Upper panel: pressure dependence of T_{LT} (full squares), T_c (onset) (empty squares) and T_{ω_0} (full triangles). For $P < P_s$, $dT_{\text{LT}}/dP = -11.5 \text{ K.GPa}^{-1}$ and for $P > P_s$, $dT_{\text{LT}}/dP = -66 \text{ K.GPa}^{-1}$. Lower panel: maximum of ρ_{UP} (see text) as a function of pressure. ρ_{UP} has been normalized to its value at P_0 and the continuous line is a fit to e^{-P/P_s} with $P_s = 1.5 \pm 0.1 \text{ GPa}$. Inset: T_c versus T_{LT} measured in $\text{La}_{1.85-y}\text{Eu}_y\text{Sr}_{0.15}\text{CuO}_4$ for different values of y ranging between 0.03 and 0.3 (full circles) [15] and versus pressure in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ (open circles) obtained in the present work.

high buckling amplitude.

At P_0 , we have shown that the onset of slow dynamics of the Cu 3d moments below 30K can be understood in terms of a glass-forming stripe-liquid phase. [11] Following this idea, a possible interpretation of the decrease of T_{ω_0} under pressure is that frustration causing charge stripes to freeze out into a glass is gradually released under pressure. The reduction of the structural distortion is more likely to increase the mobility of charge carriers in the CuO_2 layer, thus enhancing the fluidity of the electronic matrix. [16] This idea is also well supported by the fact that most of the reduction of the resistivity upturn is found where T_{ω_0} decreases, which implies a connection between freezing and localization of the charge carriers. Insofar as the slow dynamics is driven by slowly moving charge stripes in the CuO_2 plane, we can infer from the present data that glassiness, rather than stripes, is what dominantly competes with superconductivity in

$\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$. This leaves open the question of what makes charge stripes glassy. The pressure dependence of the glass transition temperature T_g particularly in relation to the qualitative changes occurring around P_s , remains to be investigated to test these ideas.

To conclude, we report a detailed investigation of the structural and electronic properties of a $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ single crystal under pressure by means of ^{139}La -NMR, resistivity and magnetic ac susceptibility measurements. Our primary result is clear evidence that the sharp suppression of superconductivity in $\text{La}_{1.65}\text{Eu}_{0.2}\text{Sr}_{0.15}\text{CuO}_4$ originates from anomalous long-time dynamics of the charge inhomogeneous phase. This reveals the key role of frustration in the interplay between static inhomogeneities and superconductivity in cuprates.

The work at Los Alamos National Laboratory and Brookhaven was performed under the auspices of the US Department of Energy (Contract No. DE-AC02-98CH10886).

* Present address: Laboratorium für Festkörperphysik HPF, ETH Hönggerberg CH-8093 Zürich

† Present address: Max Planck Institute for Chemical Physics of Solids, Noethnitzer Str. 40, 01187 Dresden, Germany.

- [1] J. M. Tranquada, B. J. Sternlieb, J. D. Axe, Y. Nakamura, and S. Uchida, *Nature* **375**, 561 (1995).
- [2] E. Dagotto, J. Burgy, and A. Moreo, *Solid State Communications* **126**, 9 (2003).
- [3] S. A. Kivelson, I. P. Bindloss, E. Fradkin, V. Oganesyan, J. M. Tranquada, A. Kapitulnik, and C. Howald, eprint cond-mat/0210683 (2003).
- [4] A. H. Castro Neto and C. Morais Smith, eprint cond-mat/0304094 (2003).
- [5] J. M. Tranquada, J. D. Axe, N. Ichikawa, A. Moodenbaugh, Y. Nakamura, and S. Uchida, *Physical Review Letter* **78**, 338 (1997).
- [6] M. Fujita, H. Goka, K. Yamada, and M. Matsuda, *Physical Review Letter* **88**, 167008 (2002).
- [7] J. D. Axe and M. K. Crawford, *Journal of Low Temperature Physics* **95**, 271 (1994).
- [8] B. Simović, M. Hückler, P. Hammel, B. Büchner, and A. Revcolevschi, *Physical Review B* **67**, 224508 (2003).
- [9] B. Büchner, M. Breuer, A. Freimuth, and A. P. Kampf, *Physical Review Letters* **73**, 1841 (1994).
- [10] H.-H. Klauss, W. Wagener, M. Hillberg, W. Kopmann, H. Walf, F. J. Litterst, M. Hückler, and B. Büchner, *Physical Review Letters* **85**, 4590 (2000).
- [11] B. Simović, P. C. Hammel, M. Hückler, B. Büchner, and A. Revcolevschi, *Physical Review B* **68**, 012415 (2003).
- [12] B. J. Suh, P. C. Hammel, M. Hückler, and B. Büchner, *Physical Review B* **59**, R3952 (1999).
- [13] J. Thompson, *Review of Scientific Instruments* **55**, 231 (1984).
- [14] T. Valla, A. V. Fedorov, P. Johnson, B. O. Wells, S. L. Hulbert, Q. Li, G. D. Gu, and N. Koshizuka, *Science* **285**, 2110 (1999).

- [15] M. Hücker, *Thesis* (University of Cologne, 1994).
- [16] Y. Dimashko, C. Morais Smith, N. Hasselmann, and A. Caldeira, Physical Review B **60**, 88 (1999).